

The Effect of Compatibilizer Addition on *Chlorella vulgaris* Microalgae Utilization as a Mixture for Bioplastic

Dianursanti^{1,*}, S A Khalis²

¹Chemical Engineering, Faculty of Engineering Universitas Indonesia, Depok 16424, Indonesia.

²Bioprocess Engineering, Faculty of Engineering Universitas Indonesia, Depok 16424, Indonesia.

Abstract. Nowadays, plastic waste is the biggest environmental issues. Since the usage of conventional plastic which come from synthesis polymer that can not be decomposed by decomposer. One of the solution is bioplastic. This study used *Chlorella vulgaris* and PVA as the based materials to made bioplastic. *Chlorella vulgaris* is chosen as the new potential of raw material for its high amount of biopolymer (Protein, carbs). However, Chlorella/PVA has some weakness such as poor physical- chemical properties. Compatibilizer is needed to improve the homogeneity and compatibility of natural and synthetic mixtures as both materials have different properties. This study aims to obtain the best maleic anhydrates concentration as compatibilizer for PVA-Chlorella plastic based. Maleic anhydrate-grafted PVA (PVA-g-MAH) was synthesized by blending PVA, maleic anhydrate, DMSO and KPS with temperature 120 °C. *Chlorella* was modified by mixing distilled water and glycerol. Both of them are mixed well then molding by temperature 120 °C. The addition of maleic anhydrates concentration (2%, 4%, 5% wt of PVA) respectively improve surface structure and cause increasing in tensile strength from 31.27 to 42.25 kgf/cm² and also increasing elongation from 10.86 to 13.00 %. With this result, it can be indicated that compatibilizer addition can improve the homogeneity and elasticity the mixture of PVA-Chlorella plastic film.

Keywords: *Chlorella vulgaris*; PVA; Compatibilizer; Maleic anhydrates; Bioplastic

1 Introduction

Petroleum based plastic is a material that is often used in everyday life. Most of them are usually disposable like packaging and they will become plastic wastes. Plastic consumption is expected to keep increasing along with the increase of public plastic demand that will lead to accumulation in plastic landfills (Wisojodharmo, 2001)[1]. Conventional plastics constituents comprising of toxic chemicals have negative impacts such as water, land, and air pollution around landfill.

The alternative that can be done is to modify or replace plastic raw material (fossil based) with other environmentally friendly such us biodegradable plastic made of renewable material of fossil based but with the combination biodegradable additives. Natural additives can be used as mixture or raw material are polysaccharides comprising starch, lignin-cellulose, pectin, and chitosan and protein and lipid derived from animals that produce casein, collagen, and gelatin. The use of those materials as plastic constituents however compete with food application.

Microalgae is a potential additive as biodegradable plastic constituent. The benefit of using microalgae for producing plastic is greater than terrestrial crops, such as higher yield, faster growth, sea water and fresh water can be used as medium, does not compete with food application, few water consumption, and production costs are relatively low (Guerrero, 2007)[2]. The microalgae that have big potential as plastic constituent is from green algae (Chlorophyte) because of its high protein content and renewable biopolymers.

Chlorella vulgaris is a green microalga with high protein content, around 51% -58% dry base. *Chlorella vulgaris* also has crack resistance because of its round shape and hard cell wall consist of cellulose and pectin (Isnanstevo et al., 1995)[3]. The thermal stability of *Chlorella vulgaris* also higher than other microalgae such as *Spirulina plantesis* (Zeller et al., 2013)[4]. In addition, microalgae has fairly small cell size, thus there is no need to isolate the protein from microalgae. These properties allow them to be relatively suitable for plastic fabrication without any prior treatment, making scalable production more cost effective.

PVA or polyvinyl alcohol is selected as a mixed polymeric material in the preparation of this bioplastic.

* Corresponding author: dianursanti@yahoo.com

Commercially, polyvinyl alcohol is the most important plastic in the manufacture of water-soluble films. It is characterized by its ability in film formation, emulsifier, and its adhesive properties. The function of adding PVA as a mixture of bioplastic preparations is to increase strength, flexibility, and durability and as a mixture with *Chlorella vulgaris* biopolymer.

Despite the numerous advantages of PVA, it does not possess thermoplastic properties and cannot be used directly as packaging material. In addition, its end products have poor surface, dimensional stability and mechanical properties. It is shown in the research done by Zhu et al. (2017)[5] is about compatibilizer addition. Polybutylene succinate (PBS) is modified with maleic anhydride into PBS-g-MA as compatibilizer in PBS and *Spirulina plantesis* mixing. The results show that compatibilizer addition can improve morphology surface from cracking, decrease pores and also increase mechanical properties.

The use of compatibilizer in the mixture with *Chlorella* and PVA plays an important role in improving mechanical characteristic of the mixture such as tensile strength and elongation. It can help to make interfacial bonding between polymer and biopolymer to homogeneity the mixture. Maleic anhydrides has been used to grafted another polymer such as LDPE, HDPE and PBS to blend with starch and *Spirulina plantesis*. So far, maleic anhydride has not been used as a compatibilizer for fabrication PVA/*Chlorella* biocomposites. This study aims to develop PVA/*Chlorella* biocomposites. So, it can be the viable and sustainable source for replacing or complementing the petroleum based plastic. The effects of compatibilizer on PVA/*Chlorella* plastic were evaluated by tensile strength, elongation and morphological properties.

2 Methods

2.1 Materials

Microalgal biomass species *Chlorella vulgaris* were used to determine their potential for bioplastic production. *Chlorella vulgaris* powder was purchased from Shaanxi Jintai Biological Engineering Co., Ltd., (China). According to company's compositional information *Chlorella* consist of 58.5% protein (on dry weight basis). Polyvinyl alcohol was purchased from PT. Brataco, with molecular weight 37000 g/mol. Maleic anhydrides (MA), Potassium peroxydisulfate (KPS) and Glycerol with a purity 99.5% were purchased from Sigma-Aldrich

2.2 Synthesis of PVA-g-MA

The synthesis of PVA-g-MA was performed as describe previously. Briefly, PVA (2.5 g) and Maleic anhydrides with (2%, 4%, 6% of PVA) in 15 ml DMSO were melt blending at 80 °C for 30 min. Afterward, KSP (1% of PVA) added into the mixture and temperature increased to 120 °C. After DMSO was evaporated and the mixture

completely homogeneous, then the mixture of PVA-g-MA was cooled at room temperature.

2.3 Preparation of Thermoplastic *Chlorella*

15% Glycerol from 5 gr algae wt added into 15 mL of distilled water and stirrer at 60 °C for 10 min. Then 5 gr *Chlorella vulgaris* was added and mixed under stirring for 30 min, at the temperature 100 °C.

2.4 Preparation of Bioplastic Samples

PVA-g-MA and thermoplastic *Chlorella* (TPC) were mixed afterward, under stirring for 30 min, at the temperature 120 °C. Then the mixture was stored for 24 hour. The mold was made of glass, sized 10 x 20 cm. The mixture was stirred and heated at 120 °C for 10 min before poured onto mold. After that, the sample were placed into oven for 15 min at 100 °C. After the samples were cooled for 10 min the samples were removed from glass.

2.5 Mechanical Properties

Mechanical properties of the bioplastic film that analysed were tensile strength and elongation according to ASTM D822. Tensile strength was the maximum load where the specimen can hold its shape before failure. Elongation was the ratio between maximum length of specimen before failure and its initial length. These characteristics usually showed in stress-strain diagram.

2.6 Electron Microscopy

Scanning electron microscopy (SEM) was used to investigate the PVA-g-MA/*Chlorella* bioplastic. Liquid nitrogen frozen fractured surfaces and tensile fractured surfaces of the composites were dried and sputter-coated with gold prior to examination. The sample chosen is the one with best mechanical properties with magnification 500x and 6000x.

3 Result and Discussion

3.1 General Appearance of Film

Figure 1 shows the photographic images of film from PVA/*Chlorella* blending with variations of compatibilizer concentration, whereas, Table 1 describes their visual appearance by researches evaluation. Film prepared were observe on the surface of the films. This observation could be indicated to the homogeneity of PVA/*Chlorella* film resultant.



Figure 1. Bioplastic film using different concentration of glycerol (a), PC (b), PCM2 (c), PCM4 and (d) PCM6

Tabel 1. Appearance of film plastic

Sample	Compatibilizer Concentration* (%)	Appearance Film
PC	-	Rough, brittle, fragile, many pores, less flexible, very difficult to peel
PCM2	2	Less pores, more flexible, less rough than without, difficult to peel
PCM4	4	Less pores than M2, slightly elastic, easy to peel
PCM6	6	No pores, more flexible, more elastic, easy to peel

3.2 Mechanical Properties of Film

This test aims to determine the characteristics of mechanical properties of bioplastic films. Testing of bioplastic mechanical properties is the most important test for knowing the homogeneity of a mixture between polymeric and biopolymer materials. The tests performed are on tensile strength and elongation.

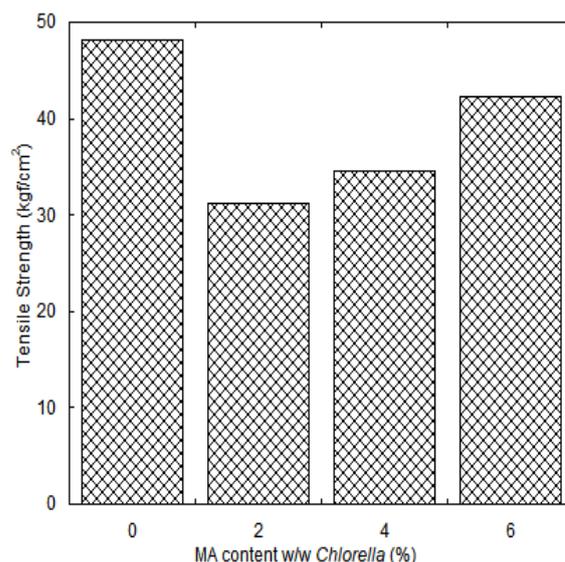


Figure 2. Effect of compatibilizer in mechanical properties for Tensile strength

Figure 2 shows samples without using compatibilizer do show the highest tensile strength value. However, after the addition 2% of maleic anhydride the value of tensile strength tends to decrease. The occurrence of a drop in tensile strength after maleic anhydride addition as a compatibilizer or the connecting compound is suspected because the thermoplastic Chlorella (TPC) in sample control (without compatibilizer) has not been fully homogenized with PVA or has not formed a bond between the TPC and the PVA polymer. Thus, the resulting plastic tends to be rigid, hard and there are still granules. Meanwhile, after the addition 2% of compatibilizer it is assumed that the polymerization reaction between TPC (biopolymer) and PVA (polymer) has been occurs, it characterized by a decrease in the value of tensile strength. Then, the value of tensile strength continues to increase as the addition of maleic anhydride 4% and 6% respectively. This may indicate that the dispersion of anhydrous groups is more prevalent in the polymer-biopolymer or it can be said that the interaction bond between Chlorella, PVA and MA is increasing. Overall increase in maleic anhydrides concentration tends to increase the tensile strength value of the bioplastic film formed. This is because the anhydra group at MA is highly reactive to the hydroxyl group present in *Chlorella vulgaris* and causes many bonds formed between thermoplastic *Chlorella vulgaris* and PVA, resulting in very strong interactions between the two polymer matrices.

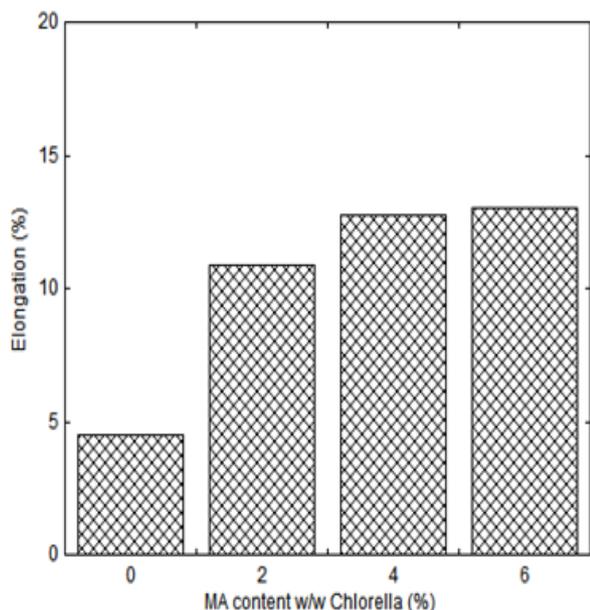


Figure 3. Effect of compatibilizer in mechanical properties for Elongation

Figure 3 shows the increase of compatibilizer concentration from 2% to 6% also significantly cause increasing film elongations from 10.86% to 13.0%. The increased value of elongation percentage due to the presence of maleic anhydrides caused polymer blends with different properties (PVA/Chlorella) to become more homogeneous so it would may causes increased the flexibility or elasticity and decrease the stiffness of the formed film mixture. It was also suggested by Chen et al. (2005) in Waryat (2013)[6] suggesting that the presence of a connecting compound or compatibilizer not only increases the mechanical strength but also the dispersion and adhesion forces between the biopolymer and the polymer.

3.3 Scanning Electron Microscopy of Film

Figure 4 and 5 shows the surface film without maleic anhydride as compatibilizer. It can be seen surface area looks so rough, there are so many pores and granules or uneven on the surface area. Also in some part it shows there were some impurities.

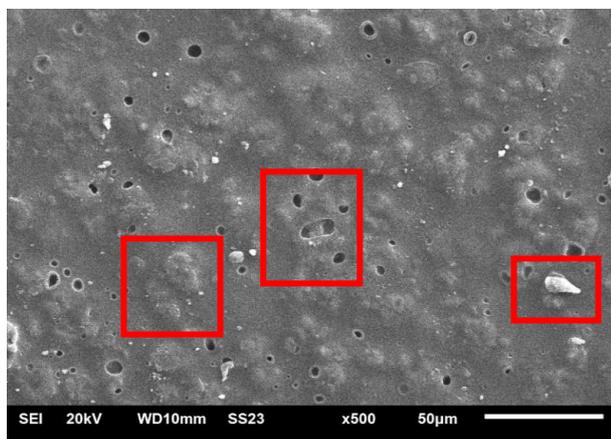


Figure 4. Surface film without compatibilizer

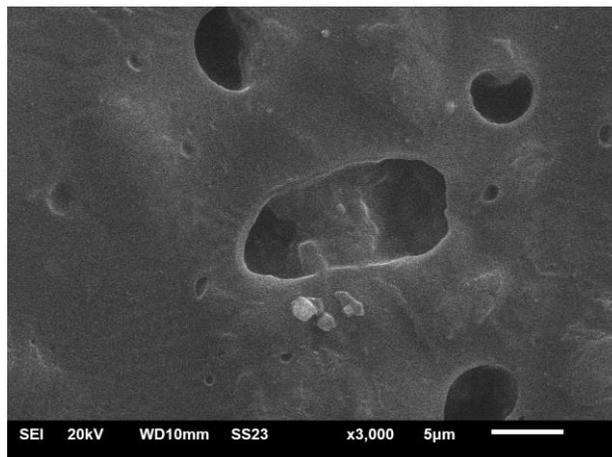


Figure 5. Surface film without compatibilizer (x3000)

Meanwhile figure 6 shows the surface area film with compatibilizer 6%. Addition of maleic anhydrides as compatibilizer to the plastic mixture helps in solubilizing between chlorella and PVA granules completely; enhances the smoothness and cohesiveness of film surface microstructure promotes homogeneous, compact the composites, and dense film surface. Also, as we can see from the figure below there is no cracks or pores in surface area.

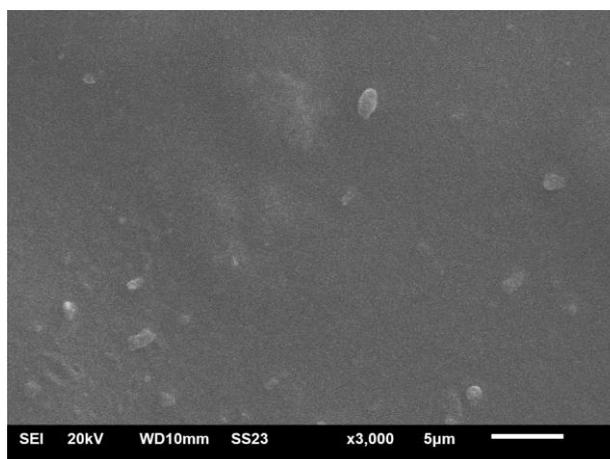
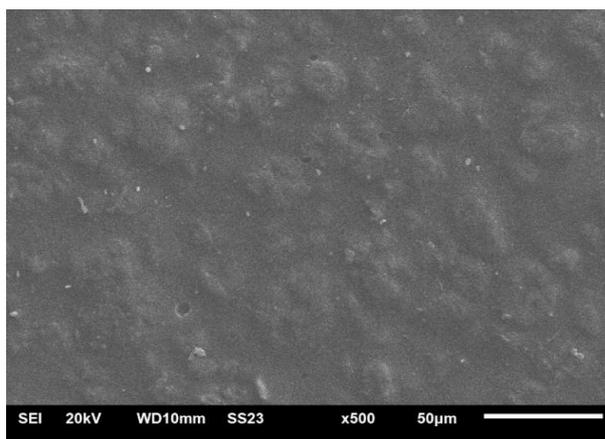


Figure 6. Surface film with compatibilizer 6%

4 Conclusion

The addition of compatibilizer can improve the morphological surface from PVA/Chlorella composites. Meanwhile, the different concentration of compatibilizer in the film forming solution have remarkable effects on the physical, tensile strength and elongation properties of the resulting films. In all the bioplastic films, the tensile strength increased with compatibilizer content from 2% to 6% and elongation also is increasing. So far, bioplastic with concentration 6% of compatibilizer chosen as the best morphological and mechanical properties because it has the best surface area and has high tensile strength and the highest value of elongation from other sample. Therefore, another test is needed to determine what the best concentration for mixing PVA-g-MA/chlorella bioplastic.

5 Aknowledgment

We gratefully acknowledge University of Indonesia for the commonwealth awarded to the first author and for funding this project through the Research Grant Scheme from *Publikasi Internasional Terindeks untuk Tugas Akhir Mahasiswa* (PITTA) grant (No.2416/UN2.R3.1/HKP.05.00/2018).

References

1. Wisojodharmo, L. A. (2001, Agustus 8). "Upaya Penanganan Limbah Plastik Di Indonesia Dan Di Dunia".pp 12-19.
2. Guerrero, M. G. (2007). Outdoor Cultivation Of Microalgae For Carotenoid Production: Current State And Perspective. *Applied Microbiology And Biotechnology*, pp 1163-1174.
3. Isnansetyo, A., & Kurniastuti. (1995). Teknik Kultur Phytoplankton Zooplankton Pakan Alami Untuk Pembenihan Organisme Laut. *Kanisius*, 116.
4. Zeller, M. A., Hunt, R., Jones, A., & Sharma, S. (2013). Bioplastics And Their Thermoplastic Blends From Spirulina And Chlorella Microalgae. *Journal Of Applied Polymer Science*, 000-000.
5. Zhu, N., Ye, M., & Chen Mingqing. (2017). Reactive Compatibilization Of Biodegradable Poly(Butylene Succinate)/Spirulina Microalgae Composites. *Macromolecular Research*, 25(2), 165-171.
6. Waryat. (2013). *Rekayasa Proses Produksi Bioplastik Berbahan Baku Pati Termoplastik Dan Polietilen*. Bogor: Institut Pertanian Bogor.