

Adsorption of crystal violet dye by biochar made from coffee ground

Le Hong Phuc^{1,#}, Nguyen Quan Hien^{1,#}, Bui Thi Hoa^{2,#}, Nguyen Ngoc Truc My^{3,#}, Thai Thi Kim Ngan^{3,#}, Bui Xuan Vuong^{3,*}

¹National Institute of Applied Mechanics and Informatics, Vietnam Academy of Science and Technology, 291 Dien Bien Phu, Ho Chi Minh City, Vietnam

²Faculty of Natural Sciences, Electric Power University, 235 Hoang Quoc Viet, Ha Noi City, Vietnam

³Faculty of Natural Sciences Education, Sai Gon University, 273 An Duong Vuong St., Ward 3, District 5, Ho Chi Minh City, Vietnam

*Email: bxvuong@sgu.edu.vn; #Equal contribution as the first author.

Abstract. Biochar was prepared by anaerobic heating coffee ground at 800 °C for 3 hours. The prepared sample was used to adsorb crystal violet dye in an aqueous environment. The result showed that the biochar sample had good adsorption capacity for crystal violet dye, with the maximum adsorption capacity of 128.87 (mg/g). Thus, low-cost biochar prepared from coffee grounds has great potential to be used as an adsorbent material to remove crystal violet dye in an aqueous environment.

Keywords: Biochar, crystal violet, coffee ground, adsorption, aqueous environment.

1 Introduction

Persistent organic dyes are often found in wastewater from the textile industry. A typical example is crystal violet dye (Cristal Violet – CV) ($C_{25}H_{30}N_3Cl$), a strong color pollutant that hinders light penetration through water, causing harm to organisms. In addition, some reports have shown that CV can be dangerous to humans such as respiratory and kidney failure, skin and gastrointestinal irritation, cytotoxicity, and CV is even reported to be a carcinogen [1]. Therefore, removing CV in the aquatic environment is an urgent issue to create a safe living environment for humans and organisms. Recently, biochar has been used as a friendly, inexpensive adsorbent material to remove organic dyes in the aquatic environment [2]. Although the adsorption efficiency of biochar is lower than that of activated carbon, biochar is much cheaper because of its simple fabrication process and the variety of biomass sources used to manufacture [3]. Several studies have reported on the fabrication of biochar to remove organic dyes from agricultural biomass sources such as peanut shells [4], straw [5], walnut shells [6], orange peels [7], date palm kernels [8], and cashew shells [9]. In this study, we fabricated biochar from coffee grounds using a simple thermal decomposition method, then the biochar samples were used to adsorb CV in an aqueous medium. Different parameters of the adsorption experiment such as adsorption time and initial concentration of CV were investigated. The mechanism of CV adsorption by biochar was also evaluated based on the Langmuir and Freundlich isotherm adsorption models.

2 Experiment and methods

2.1 Process of making biochar from coffee ground

The coffee ground was thoroughly washed to remove impurities and dried at 80 °C in a drying oven for 24 hours to obtain dried coffee ground. Then, the coffee ground was anaerobically calcined at 800 °C for 3 hours. At the end of the calcination process, the biochar obtained was ground in a porcelain mortar and passed through a 60 µm sieve. The manufactured biochar sample was denoted as biochar-800 °C.

2.2 Crystal violet adsorption experiment

The biochar samples were placed in Erlen flasks (250 mL capacity) containing 60 mL of crystal violet solution. The reaction flasks were sealed with ground glass stoppers and placed in a thermostatic shaking system (GFL 1083). At the

end of the reaction, centrifugation was performed to separate the solid fractions, and the solutions were used to measure the remaining CV concentration using a UV-VIS spectrophotometer. The adsorption efficiency of CV was calculated using the formula: $R = \frac{C_0 - C}{C_0} \cdot 100\%$

Where: C_0 - initial concentration; C - remaining concentration after adsorption; R - removal (%).

2.2.1 Adsorption equilibrium time

Adsorption equilibrium time was determined by the experiments at the adsorption time of 0, 10, 20, 30, 40, 50, 60, 70, 80, 90, 100, 110, and 120 minutes. The remaining parameters such as the mass of adsorbent material is 0.06 g; CV concentration is 20 mg/L; stirring speed is 150 rpm.

2.2.2 Effect of CV concentration

The experiment on the effect of CV concentration on the adsorption process of biochar material was carried out by changing the initial concentration of CV to 20, 30, 40, 50, 60, 70, 80, 90, and 100 mg/L, respectively. The remaining parameters such as the mass of adsorbent material is 0.06 g; stirring speed is 150 rpm; and reaction time is determined as the time to reach adsorption equilibrium in the above experiment.

2.2.3 Adsorption isotherm equation

The adsorption isotherm equation was constructed based on the experimental results of using biochar to adsorb CV at different concentrations. The experimental data were calculated and fitted with the Langmuir and Freundlich isotherm adsorption models as shown in equations (1) and (2).

Langmuir isotherm model:

$$\frac{C_e}{Q_e} = \frac{C_e}{Q_m} + \frac{1}{K_L \cdot Q_m} \quad (1)$$

Freundlich isotherm adsorption model:

$$\ln Q_e = \ln K_F + \frac{1}{n} \cdot \ln C_e \quad (2)$$

The Q_e value is calculated as follows:

$$Q_e = \frac{(C_0 - C_e) \cdot V}{m} \quad (3)$$

Here, C_c (mg/L) and Q_e (mg/g) represent the concentration and adsorption capacity at equilibrium, respectively; Q_m (mg/g) is the maximum adsorption capacity; K_L is the Langmuir constant, K_F is the Freundlich constant, n is the Freundlich coefficient.

3 Results and discussion

3.1 CV adsorption standard curve

The standard curve shows the relationship between CV concentration and the maximum adsorption intensity constant Abs. The standard curve was determined by measuring the UV-Vis spectrum of CV solutions at different concentrations from 1 mg/L to 15 mg/L. The UV-Vis spectrum of CV solutions and the standard curve are shown in Fig. 1. The constructed standard curve was used to determine the concentration of CV solutions after being adsorbed by biochar.

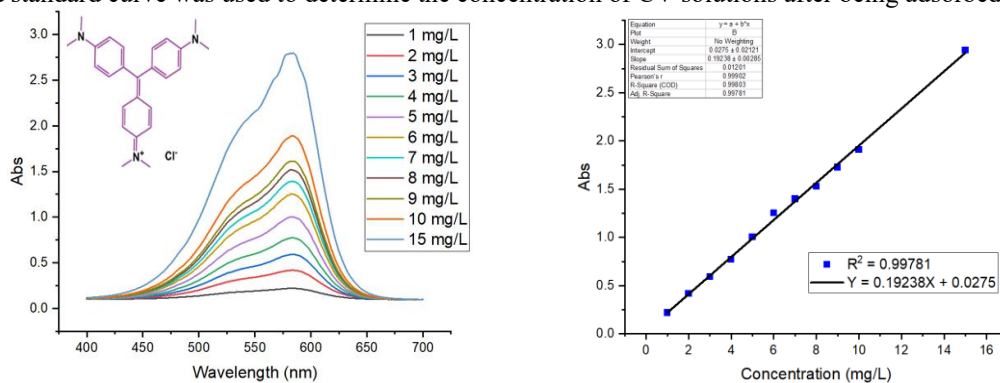


Fig. 1. UV-Vis spectra of CV solutions at different concentrations (left) and adsorption standard curve (right)

3.2 Adsorption equilibrium time

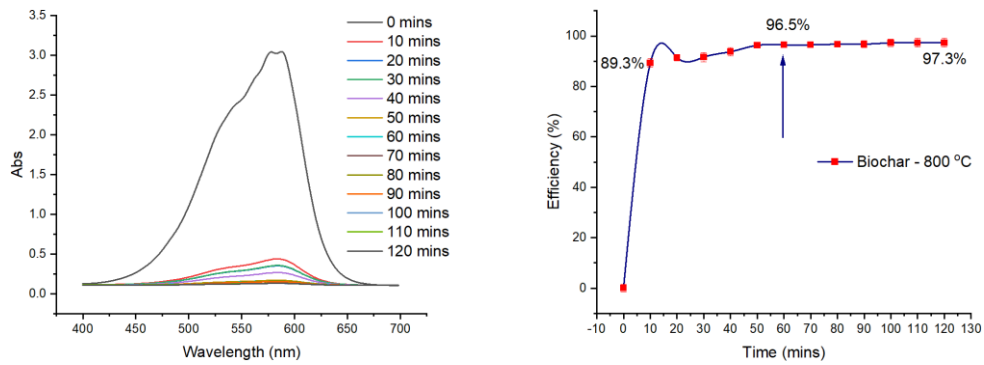


Fig. 2. UV-Vis spectra of CV solution after adsorption by biochar at different times and the dependence of adsorption efficiency on time

Figure 2 shows the results of the investigation of the adsorption capacity of CV solution according to the reaction time of biochar. It was observed that the adsorption capacity of CV dye increased rapidly in the first 10 minutes, with an adsorption efficiency of 89.3%. Next, the adsorption efficiency increased slowly and reached 96.5% at 60 minutes; after that, the adsorption efficiency almost did not increase. Thus, it can be seen that the adsorption equilibrium was reached at 60 minutes. After this time, the content of adsorbed CV remained almost unchanged because the active centers of the biochar adsorbent were completely occupied [10]. Thus, the CV adsorption capacity of biochar was quite fast in a short time of only 10 minutes, after which the adsorption rate gradually slowed down and reached equilibrium.

3.3 Adsorption capacity of biochar with CV solution at different concentrations

Fig. 3 presents the results of the investigation of the effect of the initial concentration of CV dye on the adsorption efficiency of biochar. The results show that as the initial concentration of CV dye increases, the adsorption capacity of the coal sample decreases. This is because the biochar adsorbent has enough active sites at low dye concentrations. After all, the vacant active sites on the adsorbent surface are filled with CV dye [10-11]. Surface saturation of the adsorbent may occur when the concentration of the dye increases. Saturation occurs due to the limited surface area of the adsorbent, leading to a decrease in the removal efficiency of CV dye in the aqueous environment. Although the adsorption efficiency decreases as the initial concentration of CV increases, the adsorption efficiency of the biochar sample is quite high (over 90%) for all initial concentrations of the CV solution examined, demonstrating the adsorption efficiency of CV dye by biochar in this study.

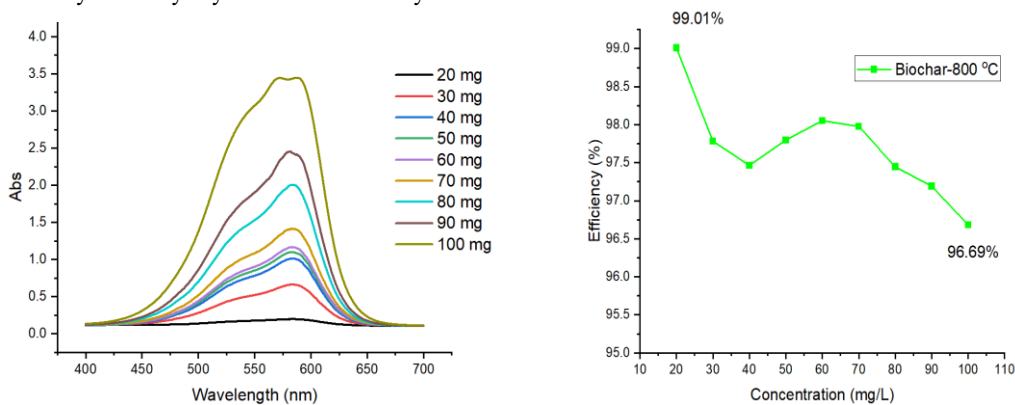


Fig. 3. CV adsorption efficiency of biochar investigated at different concentrations

3.4 Isotherm adsorption mechanism

To determine the adsorption isotherm equations, experiments using TSH to adsorb CV crystal violet solution at different concentrations were performed as shown above. Table 1 presents the experimental and calculated data to construct the Langmuir and Freundlich isotherm adsorption models. From the calculated values, the adsorption isotherms were constructed using Origin software as shown in Fig. 4. Fig. 4a shows the Langmuir isotherm adsorption model of the biochar sample. The results show that the biochar sample shows a relative agreement with the Langmuir isotherm adsorption model with a correlation coefficient value of $R^2 = 0.75509$. The linear equation $Y = AX + B$ according to the Langmuir isotherm adsorption model is $Y = 0.00776X + 0.07342$. From this equation, the maximum adsorption capacity value Q_m (mg/g) of the biochar sample can be calculated according to the formula $1/Q_m = A$ (A is the coefficient in the equation $Y = AX + B$). The calculation results show that $Q_m = 128.87$ (mg/g). The maximum adsorption capacity of the biochar sample in this study is relatively high, similar to the biochar samples reported in previous studies. Fig. 4b shows the Freundlich isotherm adsorption model of the biochar sample. The results show that the correlation coefficient R_2 is relatively high ($R_2 = 0.89289$), indicating that the CV adsorption law of the biochar sample is more consistent with the

Freundlich isotherm adsorption model. The calculated parameters such as $K_F = 17.782$ and $n = 1.81$ are quite similar to previous studies.

Table 1. Data for building Langmuir and Freundlich adsorption isotherm models

C_o	20	30	40	50	60	70	80	90	100
C_e	0.886	3.314	5.128	5.580	5.928	7.218	10.471	12.998	17.094
Q_e	19.114	26.686	34.872	44.420	54.071	62.783	69.529	77.002	82.906
C_e/Q_e	0.046	0.124	0.147	0.126	0.110	0.115	0.151	0.169	0.206
$\ln C_e$	-0.121	1.198	1.635	1.719	1.780	1.977	2.349	2.565	2.839
$\ln Q_e$	2.950	3.284	3.552	3.794	3.990	4.140	4.242	4.344	4.418

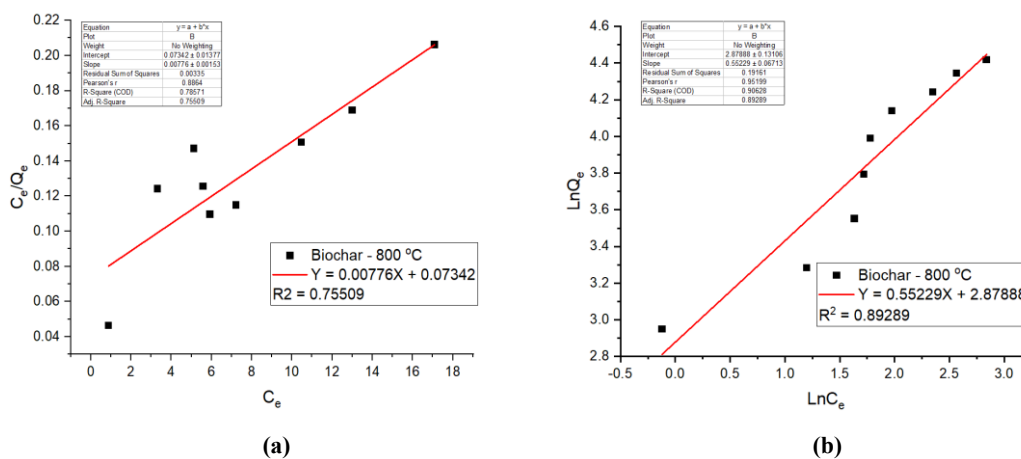


Fig. 4. Langmuir and Freundlich adsorption isotherm models of biochar

4 Conclusion

This study successfully synthesized biochar material by a simple one-stage calcination method of coffee grounds in anaerobic conditions at 800 °C. Experiments were conducted to evaluate the CV adsorption capacity of biochar in the solution environment. The results showed that the biochar sample could remove the CV crystal violet dye well with high adsorption efficiency (over 90%), and the maximum adsorption capacity reached 128.87 (mg/g). CV adsorption kinetics were studied according to the Langmuir and Freundlich isotherm adsorption models. The results showed that the biochar sample was more suitable for the Freundlich isotherm adsorption model than the Langmuir model because the correlation coefficient R^2 value was higher. Thus, biochar made from coffee grounds is a cheap adsorbent material with the potential to treat crystalline dyes in textile wastewater.

References

1. M.K. Mbacké, C. Kane, N. O. Diallo, C. M. Diop, F. Chauvet, M. Comtat, T. Tzedakis, Electrocoagulation process applied on pollutants treatment-experimental optimization and fundamental investigation of the crystal violet dye removal. *J. Environ. Chem. Eng.* **4**, 4001-4011 (2016).
2. Z. Liu, G. Han, Production of solid fuel biochar from waste biomass by low-temperature pyrolysis. *Fuel*. **158**, 159-165 (2015).
3. A. Nouioua, D. B. Salem, A. Ouakouak, N. Rouahna, O. Baigenzhenov, A. H. Bandegharai, Production of biochar from *Melia azedarach* seeds for the crystal violet dye removal from water: combining of hydrothermal carbonization and pyrolysis. *Bioengineered*. **14**, 290-306 (2023).
4. J. Song, W. Zou, Y. Bian, F. Su, R. Han, Adsorption characteristics of methylene blue by peanut husk in batch and column modes. *Desalin*. **265**, 119-125 (2011).
5. Z. Wang, P. Han, Y. Jiao, D. Ma, C. Dou, R. Han, Adsorption of congo red using ethylenediamine-modified wheat straw. *Desalin. Water. Treat.* **30**, 195-206 (2011).
6. H. Aydin, G. Baysal, Y. Bulut, Utilization of walnut shells (*Juglans regia*) as an adsorbent for the removal of acid dyes. *Desalin. Water. Treat.* **2**, 141-150 (2009).

7. R. Mane, V. Bhusari, Removal of colour (dyes) from textile effluent by adsorption using orange and banana peel. *Inter. J. Engin. Res. App.* **2**, 1997-2004 (2012).
8. K. Foo, B. Hameed, Preparation of activated carbon from date stones by microwave-induced chemical activation: Application for methylene blue adsorption. *Chem. Engin. J.* **170**, 338-341 (2011).
9. P. S. Kumar, S. Ramalingam, C. Senthamarai, M. Niranjanaa, P. Vijayalakshmi, S. Sivanesan, Adsorption of dye from aqueous solution by cashew nut shell: Studies on equilibrium isotherm, kinetics and thermodynamics of interactions. *Desalin.* **261**, 52-60 (2010).
10. A. E. Moharm, et al, Fabrication and Characterization of Effective Biochar Biosorbent Derived from Agricultural Waste to Remove Cationic Dyes from Wastewater. *Polym.* **14**, 2587 (2022).
11. P. Sudamalla, P. Saravanan, M. Matheswaran, Optimization of operating parameters using response surface methodology for adsorption of crystal violet by activated carbon prepared from mango kernel. *Sustain. Environ. Res.* **22**, 1-7 (2012).
12. Y. Kuang, X. Zhang, S. Zhou, Adsorption of Methylene Blue in Water onto Activated Carbon by Surfactant Modification. *Water.* **12**. 587-601 (2020).